

Numerical Simulation and Experimental Testing of Lightweight Ballistic Armor

Arash Ramezani and Hendrik Rothe

Chair of Measurement and Information Technology, University of the Federal Armed Forces, Hamburg, Germany

Abstract: In the security sector, the partly insufficient safety of people and equipment due to failure of industrial components are ongoing problems that cause great concern. Since computers and software have spread into all fields of industry, extensive efforts are currently made in order to improve the safety by applying certain numerical solutions. This work presents a set of numerical simulations of ballistic tests which analyze the effects of composite armor plates. The goal is to improve fiber-reinforced plastics in order to be able to cope with current challenges. Of course, the maximization of security is the primary goal, but keeping down the costs is becoming increasingly important. This is why numerical simulations are more frequently applied than experimental tests which are thus being replaced gradually.

Key words: Solver technologies, simulation models, fiber-reinforced plastics, optimization, armor systems.

1. Introduction

This work will focus on composite armor structures consisting of several layers of ultra-high molecular weight polyethylene (UHMW-PE), a promising ballistic armor material due to its high specific strength and stiffness. The goal is to evaluate the ballistic efficiency of UHMW-PE composite with numerical simulations, promoting an effective development process.

Due to the fact that all engineering simulation is based on geometry to represent the design, the target and all its components are simulated as CAD models. The work will also provide a brief overview of ballistic tests to offer some basic knowledge of the subject, serving as a basis for the comparison of the simulation results. Details of ballistic trials on composite armor systems are presented. Instead of running expensive trials, numerical simulations should identify vulnerabilities of structures. Contrary to the experimental result, numerical methods allow easy and comprehensive studying of all mechanical

parameters. Modeling will also help to understand how the fiber-reinforced plastic armor schemes behave during impact and how the failure processes can be controlled to our advantage. By progressively changing the composition of several layers and the material thickness, the composite armor will be optimized. There is every reason to expect possible weight savings and a significant increase in protection, through the use of numerical techniques combined with a small number of physical experiments.

After a brief introduction and description of the different methods of space discretization in Section III, there is a short section on ballistic trials where the experimental set-up is depicted, followed by Section V describing the analysis with numerical simulations. The paper ends with a concluding paragraph in Section VI.

2. State-of-the-Art

The numerical modeling of composite materials under impact can be performed at a constituent level (i.e., explicit modeling of fibre and matrix elements, e.g., [1]), a meso-mechanical level (i.e., consolidated plies or fibre bundles, e.g., [2]), or macromechanically

Corresponding author: Hendrik Rothe, M.Sc., lecturer, research fields: petrinets, unified modeling language.

in which the composite laminate is represented as a continuum.

In Refs. [3-6] a non-linear orthotropic continuum material model was developed and implemented in a commercial hydrocode (i.e., ANSYS® AUTODYN®) for application with aramid and carbon fibre composites under hypervelocity impact. The non-linear orthotropic material model includes orthotropic coupling of the material volumetric and deviatoric responses, a non-linear EoS (equation of state), orthotropic hardening, combined stress failure criteria and orthotropic energy-based softening. For more detail refers to Ref. [7].

Lassig et al. [8] conducted extensive experimental characterization of Dyneema® HB26 UHMW-PE composite for application in the continuum non-linear orthotropic material model, and validated the derived material parameters through simulation of spherical projectile impacts at hypervelocity. The target geometry is homogenized. The projectile is an aluminum ball in simplified terms. However, homogenized target geometries with orthotropic material models are not able to reproduce different modes of failure. The results are valid for aluminum spherical-shaped projectiles in hypervelocity range only.

Nguyen et al. [9] evaluated and refined the modeling approach and material model parameter set developed in Ref. [8] for the simulation of impact events from 400 m/s to 6,600 m/s. Across this velocity range the sensitivity of the numerical output is driven by different aspects of the material model, e.g., the strength model in the ballistic regime and the EoS in the hypervelocity regime. Here, the target geometry is divided into sub-laminates joined by bonded contacts breakable through a combined tensile and shear stress failure criterion.

The models mentioned above are valid for blunt FSP's from a velocity range of 400 to 6,600 m/s. They show considerable shortcomings in simulating pointed projectiles and thick HB26-composites.

This paper will present an optimal solution of this problem with an enhanced model for ultra-high molecular weight polyethylene under impact loading. For the first time, composite armor structures consisting of several layers of fiber-reinforced plastics are simulated for all the current military threats.

3. Methods of Space Discretization

To deal with problems involving the release of a large amount of energy over a very short period of time, e.g., explosions and impacts, there are three approaches: as the problems are highly non-linear and require information regarding material behavior at ultra-high loading rates which is generally not available, most of the work is experimental and thus may cause tremendous expenses. Analytical approaches are possible if the geometries involved are relatively simple and if the loading can be described through boundary conditions, initial conditions or a combination of the two. Numerical solutions are far more general in scope and remove any difficulties associated with geometry [10]. They apply an explicit method and use very small time steps for stable results.

For problems of dynamic fluid-structure interaction and impact, there typically is no single best numerical method which is applicable to all parts of a problem. Techniques to couple types of numerical solvers in a single simulation can allow the use of the most appropriate solver for each domain of the problem.

The goal of this paper is to evaluate a hydrocode, a computational tool for modeling the behavior of continuous media. In its purest sense, a hydrocode is a computer code for modeling fluid flow at all speeds [11]. For that reason a structure will be split into a number of small elements. The elements are connected through their nodes (see Fig. 1).

The behavior (deflection) of the simple elements is well-known and may be calculated and analyzed using simple equations called shape functions. By applying coupling conditions between the elements at their

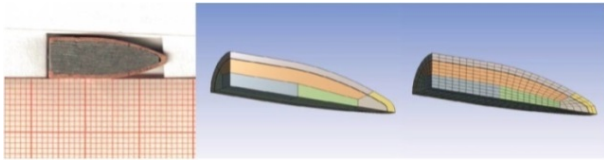


Fig. 1 Example grid.

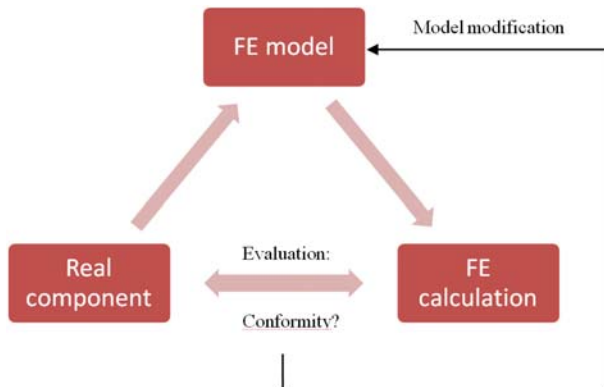


Fig. 2 Iterative procedure of an FE analysis [12].

nodes, the overall stiffness of the structure may be built up and the deflection/distortion of any node—and subsequently of the whole structure—can be calculated approximately [12].

Using a CAD-neutral environment that supports bidirectional, direct, and associative interfaces with CAD systems, the geometry can be optimized successively [13]. Therefore, several runs are necessary: from modeling to calculation to the evaluation and subsequent improvement of the model (see Fig. 2).

4. Ballistic Trials

Ballistics is an essential component for the evaluation of our results. Here, terminal ballistics is the most important sub-field. It describes the interaction of a projectile with its target. Terminal ballistics is relevant for both small and large caliber projectiles. The task is to analyze and evaluate the impact and its various modes of action. This will provide information on the effect of the projectile and the extinction risk.

Given that a projectile strikes a target, compressive waves propagate into both the projectile and the target. Relief waves propagate inward from the lateral free

surfaces of the penetrator, cross at the centerline, and generate a high tensile stress. If the impact was normal, we would have a two-dimensional stress state. If the impact was oblique, bending stresses will be generated in the penetrator. When the compressive wave reached the free surface of the target, it would rebound as a tensile wave. The target may fracture at this point. The projectile may change direction if it perforates (usually towards the normal of the target surface).

Because of the differences in target behavior based on the proximity of the distal surface, we must categorize targets into four broad groups. A semi-infinite target is one where there is no influence of distal boundary on penetration. A thick target is one in which the boundary influences penetration after the projectile is some distance into the target. An intermediate thickness target is a target where the boundaries exert influence throughout the impact. Finally, a thin target is one in which stress or deformation gradients that are negligible throughout the thickness.

There are several methods by which a target will fail when subjected to an impact. The major variables are the target and penetrator material properties, the impact velocity, the projectile shape (especially the ogive), the geometry of the target supporting structure, and the dimensions of the projectile and target.

In order to develop a numerical model, a ballistic test program is necessary. The ballistic trials are thoroughly documented and analyzed—even fragments must be collected. They provide information about the used armor and the projectile behavior after fire, which must be consistent with the simulation results (see Fig. 3).

In order to create a data set for the numerical simulations, several experiments have to be performed. Ballistic tests are recorded with high-speed videos and analyzed afterwards. The experimental set-up is shown in Fig. 4. Testing was undertaken at an indoor ballistic testing facility. The target stand provides support



Fig. 3 Ballistic tests and the analysis of fragments.

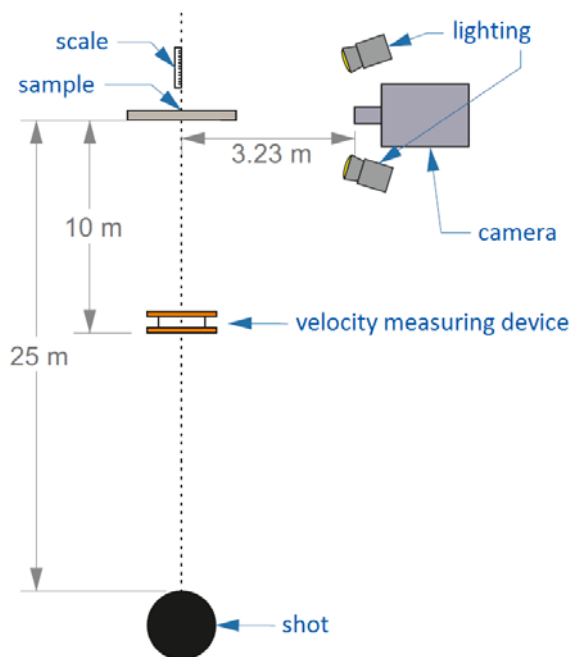


Fig. 4 Experimental set-up.

behind the target on all four sides. Every ballistic test program includes several trials with different composites. The set-up has to remain unchanged.

The camera system is a PHANTOM v1611 that enables fast image rates up to 646,000 frames per second (fps) at full resolution of $1,280 \times 800$ pixels. The use of a polarizer and a neutral density filter is

advisable, so that waves of some polarizations can be blocked while the light of a specific polarization can be passed.

Several targets of different laminate configurations were tested to assess the ballistic limit (V_{50}). The ballistic limit is considered the velocity required for a particular projectile to reliably (at least 50% of the time) penetrate a particular piece of material [15]. After the impact, the projectile is examined regarding any kind of change it might have undergone.

4. Numerical Simulation

The ballistic tests are followed by computational modeling of the experimental set-up. Then, the experiment is reproduced using numerical simulations. Fig. 1 shows a cross-section of the projectile and a CAD model. The geometry and observed response of the laminate to ballistic impact is approximately symmetric to the axis through the bullet impact point.

Numerical simulation of modern armor structures requires the selection of appropriate material models for the constituent materials and the derivation of suitable material model input data. The laminate system studied here is an ultra-high molecular weight polyethylene composite. Lead and copper are also required for the projectiles.

The projectile was divided into different parts—the jacket and the base—which have different properties and even different meshes. These elements have quadratic shape functions and nodes between the element edges. In this way, the computational accuracy, as well as the quality of curved model shapes increases. Using the same mesh density, the application of parabolic elements leads to a higher accuracy compared to linear elements (1st order elements).

4.1 Modelling

In Ref. [8], numerical simulations of 15 kg/m^2 Dyneema[®] HB26 panels impacted by 6 mm diameter aluminum spheres between 2,052 m/s to 6,591 m/s

were shown to provide very good agreement with experimental measurements of the panel ballistic limit and residual velocities (see Fig. 5). The modelling approach and material parameter set from Ref. [8] were applied to simulate impact experiments at velocities in the ballistic regime (here considered as < 1,000 m/s). In Fig. 5 the results of modelling impact of 20 mm FSPs (fragment simulating projectiles) against 10 mm thick Dyneema® HB26 are shown. The model shows a significant under prediction of the ballistic limit, 236 m/s compared to 394 m/s.

4.2 Simulation Results

Relatively newer numerical discretization methods, such as SPH (smoothed particle hydrodynamics), have been proposed that rectifies the issue of grid entanglement. The SPH method has shown good agreement with high velocity impact of metallic targets, better predictions of crack propagation in ceramics and fragmentation of composites under HVI (hypervelocity impact) compared to grid-based Lagrange and Euler methods. Although promising, SPH suffers from consistency and stability issues that lead to lower accuracy and instabilities under tensile perturbation. The latter makes it unsuitable for use with UHMW-PE composite under ballistic impact, because this material derives most of its resistance to penetration when it is loaded in tension. For these types of problems, the grid-based Lagrangian formulation still remains the most feasible for modeling UHMW-PE composite.

3D numerical simulations were performed of the full target and projectile, where both were meshed using 8-node hexahedral elements. The projectile was meshed with 9 elements across the diameter. The target is composed of sub-laminates that are one element thick, separated by a small gap to satisfy the master-slave contact algorithm (external gap in AUTODYN®) and bonded together as previously discussed. The mesh size of the target is approximately equal to the projectile at the impact site.

The mesh was then graded towards the edge, increasing in coarseness to reduce the computational load of the model. Since UHMW-PE composite has a very low coefficient of friction, force fit clamping provides little restraint.

High speed video of ballistic impact tests typically showed the action of loosening and moving clamps upon impact. As such no boundary conditions were imposed on the target. The FSP material was modelled

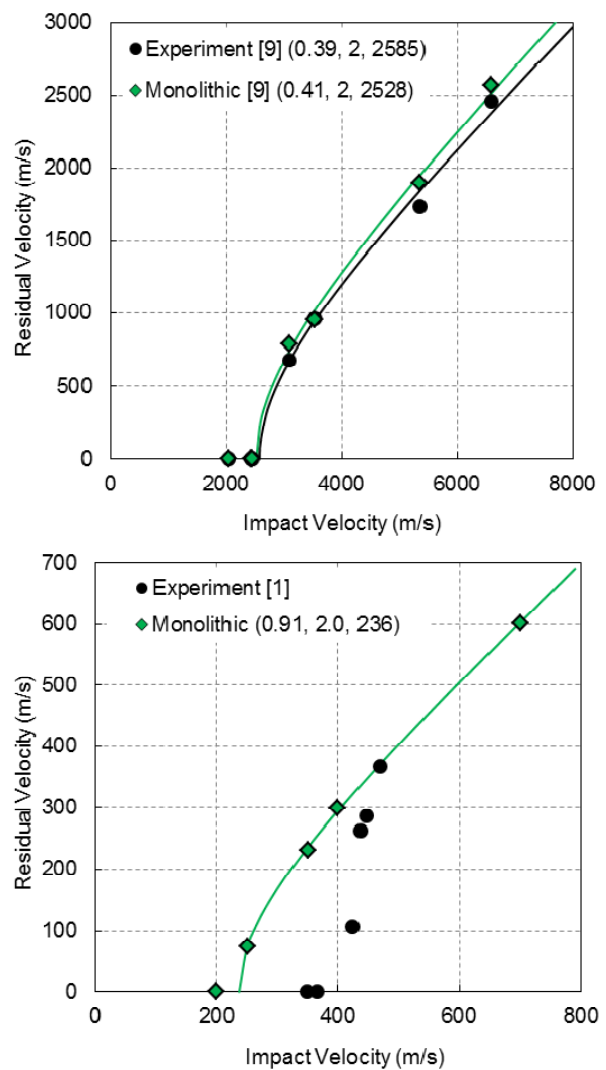


Fig. 5 Experimental and numerical impact residual velocity results for impact of 6 mm diameter aluminum spheres against 15 kg/m² Dyneema® HB26 at normal incidence (left) and impact of 20 mm fragment simulating projectiles against 10 mm thick Dyneema® HB26 at normal incidence (right). Lambert-Jonas parameters (a, p, V_{bl}) are provided in the legend.

as Steel S-7 from the AUTODYN[®] library described using a linear EoS and the Johnson-Cook strength model [16]. The aluminum sphere was modelled using AL1100-O from the AUTODYN[®] library that uses a shock EoS and the Steinburg Guinan strength model [17]. The master-slave contact algorithm was used to detect contact between the target and projectile.

The sub-laminate model with shock EoS was applied to the aluminum sphere hypervelocity impact series and 20 mm FSP ballistic impact series presented in Fig. 5, the results of which are shown in Fig. 6. The sub-laminate model is shown to provide a significant improvement in predicting the experimental V_{50} of 394 m/s for the FSP ballistic impacts (377 m/s) compared to the monolithic model (236 m/s).

The ballistic limit and residual velocity predicted with the sub-laminate model for the hypervelocity impact case are shown to be comparable with the original monolithic model. For conditions closer to the ballistic limit, the sub-laminate model is shown to predict increased target resistance (i.e., lower residual velocity). For higher overmatch conditions there is some small variance between the two approaches.

In Fig. 7, a qualitative assessment of the bulge formation is made for the 10 mm panel impacted at 365 m/s (i.e., below the V_{50}) by a 20 mm FSP. Prediction of bulge development is important as it is characteristic of the material wave speed and is also a key measure in defence applications, particularly in personnel protection (i.e., vests and helmets). The sub-laminate model is shown to reproduce the characteristic pyramid bulge shape and drawing of material from the lateral edge. In comparison, the bulge prediction of the baseline model is poor, showing a conical shape with the projectile significantly behind the apex. In the baseline model penetration occurs through premature through-thickness shear failure around the projectile rather than in-plane tension (membrane) which would allow the formation of a pyramidal bulge as the

composite is carried along with the projectile. Furthermore, in the baseline model the extremely small through thickness tensile strength (1.07 MPa) in the bulk material leads to early spallation/delamination of the back face. This allows the material on the target back face to fail and be accelerated ahead of the projectile. In the sub-laminate model, these two artifacts are addressed, and so a more representative bulge is formed.

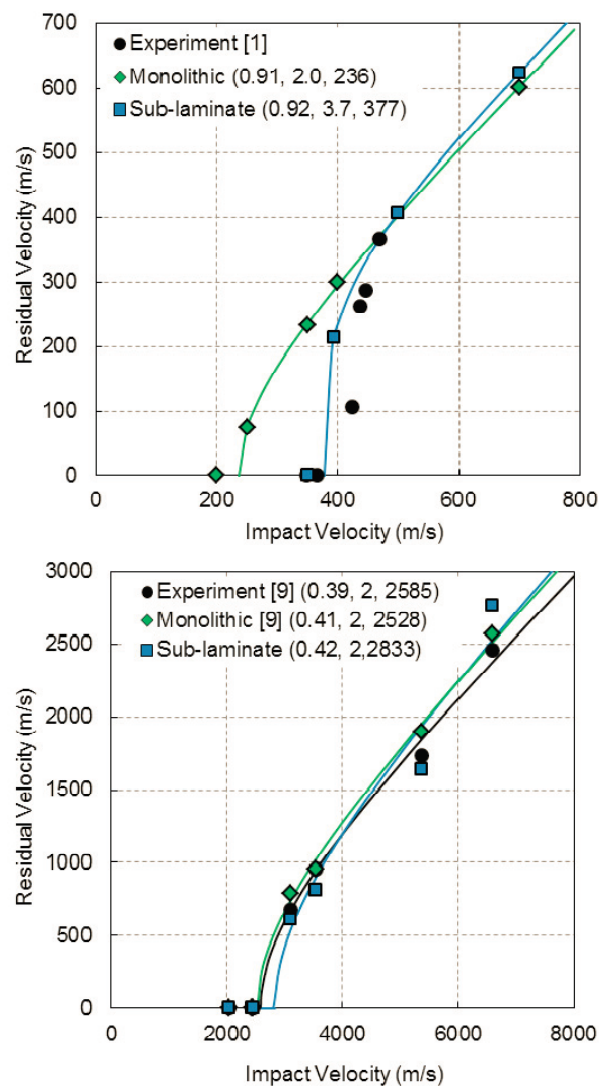


Fig. 6 Experimental and numerical impact residual velocity results for impact of 6 mm diameter aluminum spheres against 15 kg/m² Dyneema[®] HB26 at normal incidence (left) and impact of 20 mm fragment simulating projectiles against 10 mm thick Dyneema[®] HB26 at normal incidence (right). Lambert-Jonas parameters (a , p , V_{bi}) are provided in the legend.

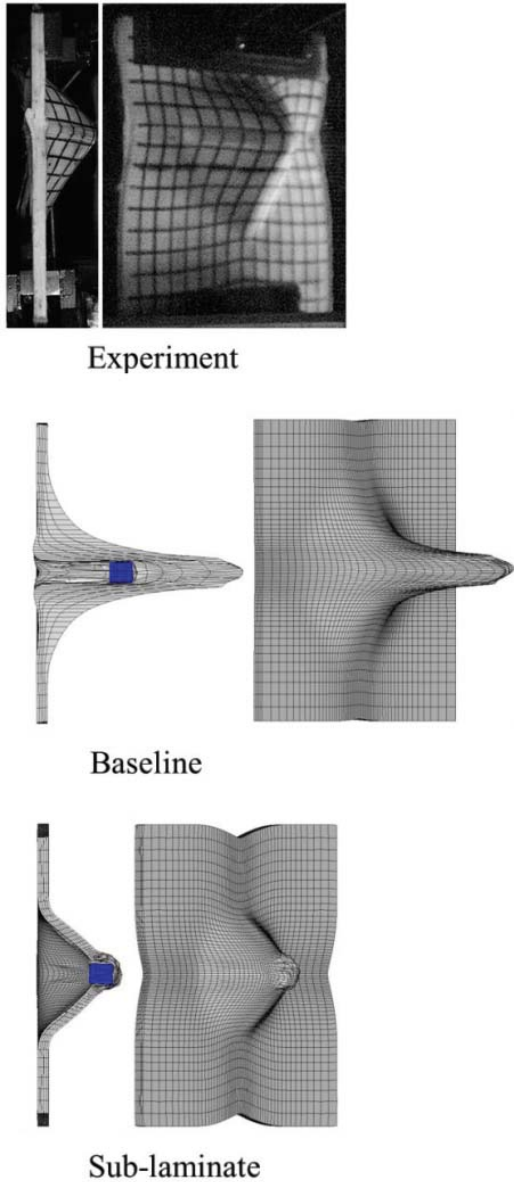


Fig. 7 Bulge of a 10 mm target impact by a 20 mm FSP at 365 m/s (experiment) and 350 m/s (simulations), 400 μ s after the initial impact.

4.3 Further Validations

The material model developed in Refs. [8] and [9] has some shortcomings regarding the simulation of handgun projectiles (see Fig. 8). The ballistic limit was significantly under predicted. Evaluation of the result suggests that the failure mechanisms, which drive performance in the rear section of the target panel (i.e., membrane tension) were not adequately reproduced, suggesting an under-estimate of the material in-plane tensile performance.

A major difficulty in the numerical simulation of fibre composites under impact is the detection of failure processes between fibre and matrix elements as well as between the individual laminate layers (delamination). One promising approach is the use of “artificial” inhomogeneities on the macroscale. Here, an alternative simulation model has been developed to overcome these difficulties. Using sub-laminates and inhomogeneities on the macroscale, the model does not match the real microstructure, but allows a more realistic description of the failure processes mentioned above.

Approaches based on the continuum or macroscale present a more practical alternative to solve typical engineering problems. However the complexity of the constitutive equations and characterization tests necessary to describe an anisotropic material at a macro or continuum level increases significantly.

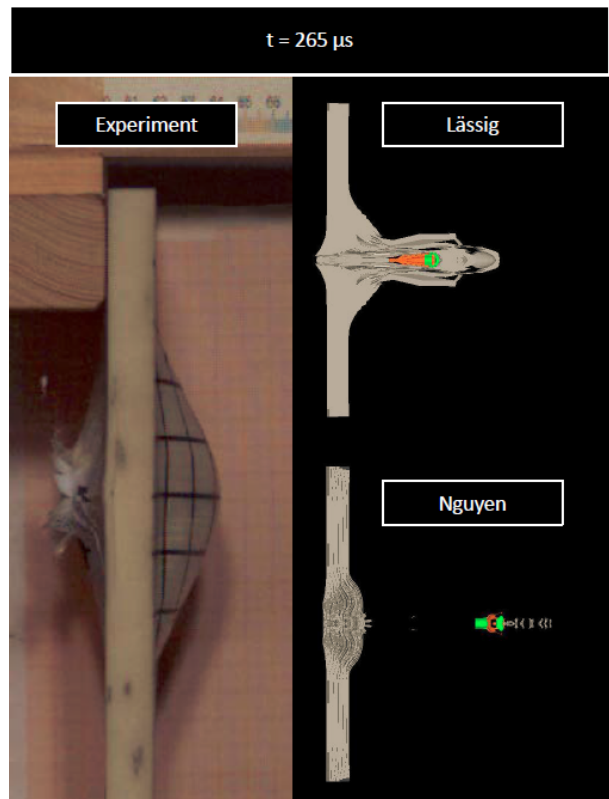


Fig. 8 Comparing experimental results with the previous simulation models of Lässig [8] and Nguyen [9], 265 μ s after impact (grey = plastic deformation, green = elastic deformation, orange = material failure); projectile velocity: 674 m/s; target thickness: 16.2 mm (60 layers of HB26).

When considering the micromechanical properties of the orthotropic yield surface with a non-linear hardening description, a non-linear shock equation of state, and a three-dimensional failure criterion supplemented by a linear orthotropic softening description should be taken into account. It is important to consider all relevant mechanisms that occur during ballistic impact, as the quality of the numerical prediction capability strongly depends on a physically accurate description of contributing energy dissipation mechanisms. Therefore, a combination of ballistic experiments and numerical simulations is required. Predictive numerical tools can be extremely useful for enhancing our understanding of ballistic impact events. Models that are able to capture the key mechanical and thermodynamic processes can significantly improve our understanding of the phenomena by allowing time-resolved investigations of virtually every aspect of the impact event. Such high fidelity is immensely difficult, prohibitively expensive or near impossible to achieve with existing experimental measurement techniques.

The thermodynamic response of a material and its ability to carry tensile and shear loads (strength) is typically treated separately within hydrocodes such that the stress tensor can be decomposed into volumetric and deviatoric components. Since the mechanical properties of fibre-reinforced composites are anisotropic (at least at the meso- and macroscale level), the deviatoric and hydrostatic components are coupled. That is deviatoric strains that will produce a volumetric dilation and hydrostatic pressure leads to non-uniform strains in the three principal directions.

The strength and failure model was investigated by modeling single elements under normal and shear stresses. It was found that under through-thickness shear stress, the element would fail prematurely below the specified through-thickness shear failure stress. It was found that if the through-thickness tensile strength was increased, failure in through-thickness

shear was delayed. This evaluation study shows the importance of the strength, failure and erosion models for predicting performance in the ballistic regime.

Previous material models for fiber-reinforced plastics were adjusted and the concept has been extended to different calibers and projectile velocities. Composite armor plates between 5.5 and 16.2 mm were tested in several ballistic trials and high-speed videos were used to analyze the characteristics of the projectile—before and after the impact.

The simulation results with the modified model are shown in Fig. 9. The deformation of the projectile, e.g., 7.62×39 mm, is in good agreement with the experimental observation.

Both delamination and fragmentation can be seen in the numerical simulation.

Compared to the homogeneous continuum model, fractures can be detected easily. Subsequently, the results of experiment and simulation in the case of perforation were compared with reference to the projectile residual velocity. Here, only minor differences were observed.

It should be noted that an explicit modeling of the individual fibres is not an option, since the computational effort would go beyond the scope of modern server systems (see Fig. 10).

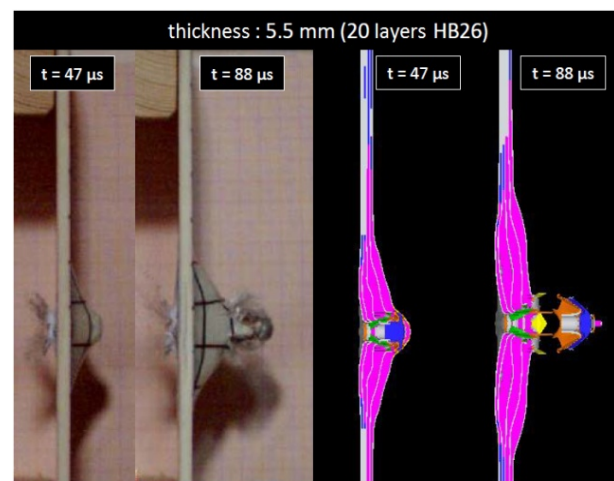


Fig. 9 Effect of a 5.5 mm target impact by a 7.62×39 mm bullet at 686 m/s, 47 μ s and 88 μ s after the initial impact.

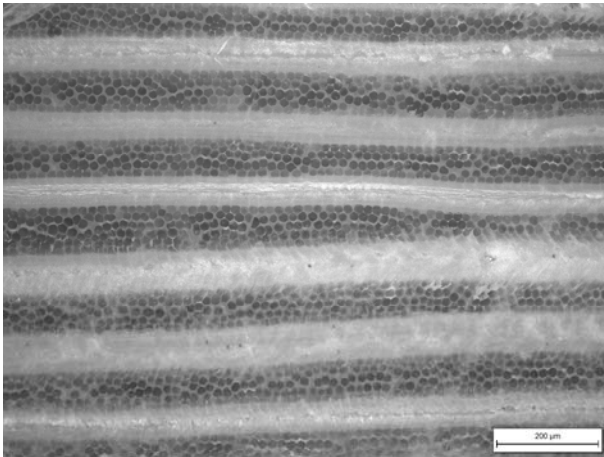


Fig. 10 Cross section of a Dyneema® HB26 panel.

5. Results and Discussion

This work demonstrated how a small number of well-defined experiments can be used to develop, calibrate, and validate solver technologies used for simulating the impact of projectiles on complex armor systems and composite laminate structures.

Existing material models were optimized to reproduce ballistic tests. High-speed videos were used to analyze the characteristics of the projectile—before and after the impact. The simulation results demonstrate the successful use of the coupled multi-solver approach and new modeling techniques. The high level of correlation between the numerical results and the available experiment or observed data demonstrates that the coupled multi-solver approach is an accurate and effective analysis method.

A non-linear orthotropic continuum model was evaluated for UHMW-PE composite across a wide range of impact velocities. Although previously found to provide accurate results for hypervelocity impact of aluminum spheres, the existing model and dataset revealed a significant underestimation of the composite performance under impact conditions driven by through-thickness shear performance (ballistic impact of fragment simulating projectiles). The model was found to exhibit premature through thickness shear failure as a result of directional coupling in the modified Hashin-Tsai failure criterion

and the large discrepancy between through-thickness tensile and shear strength of UHME-PE composite. As a result, premature damage and failure was initiated in the through-thickness shear direction leading to decreased ballistic performance. By de-coupling through-thickness tensile failure from the failure criteria and discretizing the laminate into a nominal number of kinematically joined sub-laminates through the thickness, progresses in modelling the ballistic response of the panels was improved.

New concepts and models can be developed and easily tested with the help of modern hydrocodes. The initial design approach of the units and systems has to be as safe and optimal as possible. Therefore, most design concepts are analyzed on the computer.

FEM-based simulations are well-suited for this purpose. Here, a numerical model has been developed, which is capable of predicting the ballistic performance of UHMW-PE armor systems. Thus, estimates based on experience are being more and more replaced by software.

The gained experience is of prime importance for the development of modern armor. By applying the numerical model a large number of potential armor schemes can be evaluated and the understanding of the interaction between laminate components under ballistic impact can be improved.

The most important steps during an FE analysis are the evaluation and interpretation of the outcomes followed by suitable modifications of the model. For that reason, ballistic trials are necessary to validate the simulation results. They are designed to obtain information about

- the velocity and trajectory of the projectile prior to impact,
- changes in configuration of projectile and target due to impact,
- masses, velocities, and trajectories of fragments generated by the impact process.

Ballistic trials can be used as the basis of an iterative optimization process. Numerical simulations

are a valuable adjunct to the study of the behavior of metals subjected to high-velocity impact or intense impulsive loading. The combined use of computations, experiments and high-strain-rate material characterization has, in many cases, supplemented the data achievable by experiments alone at considerable savings in both cost and engineering man-hours.

References

- [1] Segala, D. B., and Cavallaro, P. V. 2014. "Numerical Investigation of Energy Absorption Mechanisms in Unidirectional Composites Subjected to Dynamic Loading Events." *Computational Materials Science* 81: 303-12.
- [2] Chocron, S. et al. 2014. "Modeling Unidirectional Composites by Bundling Fibers into Strips with Experimental Determination of Shear and Compression Properties at High Pressures." *Composites Science and Technology* 101: 32-40.
- [3] Hayhurst, C. J., Hiermaier, S. J., Clegg, R. A., Riedel, W., and Lambert, M. 1999. "Development of Material Models for Nextel and Kevlar-Epoxy for High Pressures and Strain Rates." *International Journal of Impact Engineering* 23: 365-76.
- [4] Clegg, R. A., White, D. M., Riedel, W., and Harwick, W. 2006. "Hypervelocity Impact Damage Prediction in Composites: Part I—Material Model and Characterisation." *International Journal of Impact Engineering* 33: 190-200.
- [5] Riedel, W., Nahme, H., White, D. M., and Clegg, R. A. 2006. "Hypervelocity Impact Damage Prediction in Composites: Part II—Experimental Investigations and Simulations." *International Journal of Impact Engineering* 33: 670-80.
- [6] Wicklein, M., Ryan, S., White, D. M., and Clegg, R. A. 2008. "Hypervelocity Impact on CFRP: Testing, Material Modelling, and Numerical Simulation." *International Journal of Impact Engineering* 35: 1861-69.
- [7] ANSYS. *AUTODYN Composite Modelling Release 15.0*. [Online]. Available from: <http://ansys.com/> 2016.07.08.
- [8] Lassig, T. et al. 2015. "A Non-Linear Orthotropic Hydrocode Model for Ultra-High Molecular Weight Polyethylene in Impact Simulations." *International Journal of Impact Engineering* 75: 110-22.
- [9] Nguyen, L. H. et al. 2015. "Numerical Modelling of Ultra-High Molecular Weight Polyethylene Composite under Impact Loading." *Procedia Engineering* 103: 436-43.
- [10] Zukas, J. 2004. *Introduction to hydrocodes*. Elsevier Science.
- [11] Collins, G.-S. 2002. "An Introduction to Hydrocode Modelling." *Applied Modelling and Computation Group*. Imperial College London.
- [12] Fröhlich, P. 2005. *FEM Application Practice*. Vieweg Verlag.
- [13] Woyand, H.-B. 2007. "FEM with CATIA V5." *J. Schlembach Fachverlag*.
- [14] Frieß, R. 2008. "General Basis for Ballistic Material, Construction and Product Testing." Presented at the Ballistic Day in Ulm.
- [15] Carlucci, D. E., and Jacobson, S. S. 2008. *Ballistics: Theory and Design of Guns and Ammunition*. CRC Press.
- [16] Johnson, G., and Cook, W. 1983. "A Constitutive Model and Data for Metals Subjected to Large Strains, High Strain Rates and High Temperatures." *In 7th International Symposium on Ballistics*, 541-7.
- [17] Steinberg, D. 1996. *Equation of State and Strength Properties of Selected Materials*. California.